

Influence of surface anisotropy on the magnetization reversal of nanoparticles

Òscar Iglesias ^{*1} and Amílcar Labarta¹

¹ Departament de Física Fonamental, Universitat de Barcelona, Diagonal 647, 08028 Barcelona, Spain

Received May 2004, revised XXX, accepted XXX

Published online XXX

PACS 05.10.Ln, 75.40.Cx, 75.40.Mg, 75.50.Gg, 75.50.Tf, 75.60.Ej

The influence of surface anisotropy on the magnetization processes of maghemite nanoparticles with ellipsoidal shape is studied by means of Monte Carlo simulations. Radial surface anisotropy is found to favor the formation of hedgehog-like spin structures that become more stable as the surface anisotropy constant at the surface k_S is increased from the value at the core. We have studied the change in the low temperature hysteresis loops with the particle aspect ratio and with k_S , finding a change in the magnetization reversal mode as k_S or the particle elongation is increased.

Copyright line will be provided by the publisher

1 Introduction

Most spins in a magnetic nanoparticle are at the particle surface where the reduced coordination and the broken translational symmetry of the lattice are responsible for changes in some local physical properties of the material. Among them, there is the reduction in exchange interaction constants and the increased local anisotropy at the particle surface with respect to bulk values [1] phenomenological model that described this last phenomenon was first introduced by Néel in [2], but experimental determination of the microscopic structure and properties of the surface of nanoparticles is still a challenge to be solved. For example, an estimate of the surface anisotropy constant can only be extracted indirectly from magnetic measurements by fitting to an effective anisotropy constant [3]. However, there are increasing evidences from experiments that surface effects play a dominant role in the anomalous low temperature magnetic properties of nanoparticle systems [4]. Therefore, simulations of magnetic properties in which microscopic parameters extracted from experiments are used [5, 6, 7] may serve as a benchmark to test the phenomenological models at hand. In this article, we use the Monte Carlo method to simulate the magnetization processes of individual nanoparticles modeled by classical Heisenberg spins on the maghemite lattice with radial surface anisotropy k_S different from that on the core.

2 Model and simulation method

The model considered is an extension to Heisenberg spins of our previous MC simulation for an Ising spin model of a γ -Fe₂O₃ (maghemite) particle [8]. The particles considered have spherical or ellipsoidal shape with diameter $D = 3$ and elongations $L = 3 - 8$ (in units of the cell size a), containing from $N = 347$ to 883 spins. The surface spins of the particle are considered to be those on the outer unit cell and have anisotropy constant k_S and radial local anisotropy axes along the directions $\mathbf{n}_i$, whereas core spins have uniaxial anisotropy k_C pointing along the z-axis. Indirect estimations of the anisotropy constants yield

* Corresponding author: e-mail: oscar@ffn.ub.es, Phone: +34 93 4021155, Fax: +34 93 4021149

values in the range $k_C = 0.01 - 1$ K, $k_S = 1 - 100$ K, so we will fix $k_C = 1$ K and vary only k_S . The interaction Hamiltonian in temperature units can be written as

$$H/k_B = - \sum_{\langle i,j \rangle} J_{ij} \vec{S}_i \cdot \vec{S}_j - \sum_{i=1}^N \vec{h} \cdot \vec{S}_i - \sum_{i=1}^{N_{Core}} [k_C (S_i^z)^2] + \sum_{i=1}^{N_{Surf}} [k_S (\vec{S}_i \cdot \hat{n}_i)^2] . \quad (1)$$

In the first term, J_{ij} are the nearest-neighbours exchange constants among the spins in the two sublattices with different coordination of maghemite, all of them are antiferromagnetic, being J_{TO} the strongest in magnitude and making maghemite a ferrimagnetic compound [9]. We have computed equilibrium configurations by starting from a disordered state at a high temperature and decreasing the temperature in steps $dT = 1$. Hysteresis loops are started from a saturating field along the core easy-axis that is decreased in steps $dh = -1$, during which the magnetization is averaged over 1000 MC steps. In both cases, the standard MC method for continuous spins has been used with a trial jump consisting in a combination of uniform and small angle around the current spin direction that allows to obtain reliable simulations for treat the weak and strong anisotropy cases with the same algorithm, see [10] for the details.

Fig. 1 Equilibrium spin configurations of an ellipsoidal maghemite particle with radial surface anisotropy, diameter $D = 3a$ and elongation $L = 8a$, achieved after cooling from high temperature to $T = 0$. Upper (lower) panels are cross-sections along the equatorial plane (long-axis) showing only the spins on the central unit cell.

3 Results

In Fig. 1, we show snapshots of the spin configurations attained after the cooling process previously described, for several values of the surface anisotropy constant k_S . The pictures present a cut of one unit cell width along the equatorial plane and along the major axis of the particle. For values of k_S smaller than a certain critical value k_S^* (which depends on the particle size and on the shape), the radial anisotropy at the surface is not strong enough to cant the core spins towards the radial direction. Therefore, the core spins are antiferromagnetically aligned with a small net magnetization component along the z axis due a small number of non-compensated spins (see Fig. 1 for $k_S = 10$). However, at the particle surface, the spins present already a high degree of disorder due to the competition between the reduced local exchange field (locally reduced with respect to that on the core spins) and the anisotropy, inducing some degree of frustration at the surface. As k_S is further increased (see Fig. 1 for $k_S = 20$), the disorder of the surface spins is transmitted to the particle core and results in the departure of core spins from the local anisotropy axis towards the radial direction. Finally, when anisotropy dominates over exchange energy ($k_S > k_S^*$, see Fig. 1 for $k_S = 100$), the hedgehog-like structures are formed, with the spins pointing along the local radial direction and having antiparallel orientations with the nearest neighbors on the other sublattice.

We have also studied the influence of surface anisotropy and particle shape on the magnetization reversal processes. For this purpose, zero temperature hysteresis loops have been simulated using the procedure described previously for ellipsoidal particles with elongations $L = 3 - 8$ and diameter $D = 3$. Some selected results are presented in Fig. 2, where the total magnetization component along the field direction (left panels) is shown together with the contribution of the surface and core spins to $M_n = \sum_{i=1}^N |\vec{S}_i \cdot \hat{n}_i|$, the sum of the projections of spins onto the local anisotropy axis (central and right panels). By comparing the loops for $k_S = 10$ to those for $k_S = 100$, we see that the coercive field increases and the remanence decreases with increasing surface anisotropy, independently of the elongation L of the particle. Moreover, the presence of disordered groups of spins at the surface induced by surface anisotropy makes the loops more elongated and increases the closure fields of the loops as found also in experiments on ferrimagnetic oxides [11]. The rounding of the loops near the coercive field clearly indicates a progressive departure from a uniform reversal mechanism with increasing k_S . When looking only at the M_z component, not much

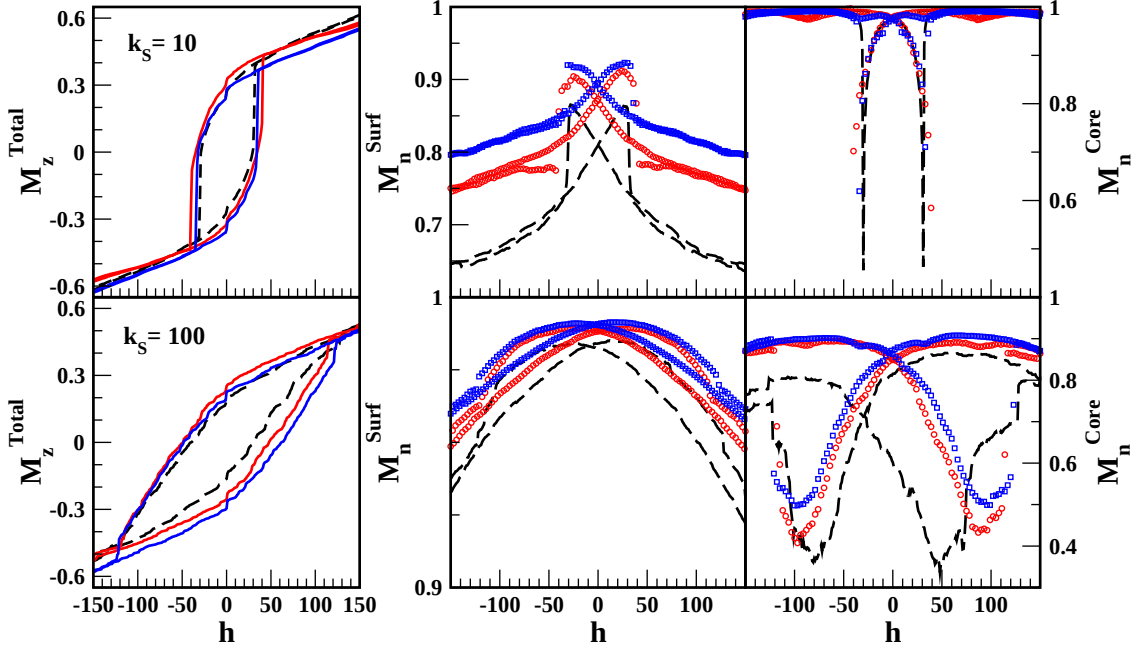


Fig. 2 Hysteresis loops for ellipsoidal particles with two values of the radial surface anisotropy constant $k_S = 10, 100$. Dashed lines are for a spherical particle with diameter $D = 3$, red circles and blue squares for an ellipsoidal particle with $D = 3$ and $L = 6, 8$ respectively. Left panels display the total magnetization while central and right panels show the surface and core contributions to M_n , the sum of projections of the magnetization in to the local easy-axis directions.

difference is appreciated between the loops for particles with different L because of the compensation of the spin components transverse to the field direction due to the symmetry of revolution of the particles around the z axis. However, upon further inspection of the M_n^{Surf} and M_n^{Core} contributions and animated snapshots taken along the loops [12], the details of the reversal process can be better understood. Let us notice first that, when k_S is increased from k_S^* , the reversal mechanism changes from quasi-uniform (induced by the core) rotation at low k_S values, to a process in which the formation of surface hedgehog-like structures induce the non-uniform switching of the whole particle. In the first regime ($k_S = 10$ case in Fig. 2), the core and surface spins point mostly along the z axis ($M_n^{Core} \sim 1$, $M_n^{Surf} \ll 1$) except near the coercive field, where they make short excursions towards the radial direction driven by the surface anisotropy (see the dips in M_n^{Core} and the cusps in M_n^{Surf}). However, for $k_S \gtrless k_S^*$ ($k_S = 100$ case in Fig. 2), surface spins remain near the local radial easy-directions ($M_n^{Surf} \sim 1$) during the reversal, while the core spins are dragged out the z local easy-axis by the surface spins during the reversal, except for values of h near the closure field. This is indicated by the widening of the dips in M_n^{Core} and the global decrease of M_n^{Core} values as k_S increases. Finally, let us remark also that, for all the k_S considered, the M_n^{Surf} values along the whole hysteresis loops increase with increasing L , which indicates that the surface spins remain closer to the local radial direction during the reversal as particles become more elongated. When increasing L , the dips in M_n^{Core} become less profound for $k_S > k_S^*$, and indication that reversal of core spins along the radial direction is suppressed by the elongation. However, for weak anisotropy ($k_S < k_S^*$), the more elongated the particles are, the greater the deviation of surface spins towards the radial direction during the reversal.

Acknowledgements We acknowledge CESCO and CEPBA under coordination of C⁴ for computer facilities. This work has been supported by the Spanish SEEUID through the MAT2003-01124 project and the Generalitat de Catalunya through the 2001SGR00066 CIRIT project.

References

- [1] P. Tartaj *et al.*, Phys. Rev. B **69**, 094401 (2004).
- [2] L. Néel, J. Phys. Radium **12**, 339 (1951).
- [3] F. S. Bødker, S. Mørup, and S. Linderøth, Phys. Rev. Lett. **72**, 282 (1994).
- [4] X. Batlle and A. Labarta, J. Phys. D: Appl. Phys. **35**, R15 (2002).
- [5] K. N. Trohidou, X. Zianni, and J. A. Blackman, J. Appl. Phys. **84**, 2795 (1998).
- [6] H. Kachkachi and M. Dimian, Phys. Rev. B **66**, 174419 (2002).
- [7] Y. Labay *et al.*, J. Appl. Phys. **91**, 8715 (2002).
- [8] O. Iglesias and A. Labarta, Phys. Rev. B **63**, 184416 (2001).
- [9] R. H. Kodama and A. E. Berkowitz, Phys. Rev. B **59**, 6321 (1999).
- [10] O. Iglesias and A. Labarta, Physica B **343**, 286 (2004).
- [11] B. Martínez *et al.*, Phys. Rev. Lett. **80**, 181 (1998).
- [12] Animated snapshots of the configurations along the hysteresis loops can be found at the web site: <http://www.ffn.ub.es/oscar/SCM2004/SCM2004.html>.

This figure "Fig_1.gif" is available in "gif" format from:

<http://arXiv.org/ps/cond-mat/0407176v1>